## GOVERNMENT OF INDIA MINISTRY OF RAILWAYS (Railway Board)



### INDIAN RAILWAY STANDARD SPECIFICATION FOR END FORGING OF THICK WEB ASYMMETRICAL RAILS

**SERIAL NO. T-62** 

January, 2025

## Issued by

RESEARCH DESIGNS & STANDARDS ORGANISATION (MINISTRY OF RAILWAYS)
MANAK NAGAR, LUCKNOW – 226011

#### 0. FOREWORD

O.1 This specification issued under the fixed serial number as Indian Railway Standards Specification, IRS:T-62; the final number indicates the year of original adoption as standard, or in the case of revision, the year of last revision.

Adopted 2022

Revised 2024

0.2 This standard specification is intended to cover the technical provisions relating to End Forging of Thick Web Asymmetrical Rails at the End Forging plant. The process verification of the End Forging plant shall be carried out by RDSO as per the Inspection Regime for End Forged Asymmetrical Rails of ZU-1-60 /60E1A1 & ZU-2-49/49 E1A1 rail profile to 60 kg (UIC)/60E1& IRS 52 Kg rail profile.

#### 1.0 SCOPE

This specification covers technical requirements for end forging of 880/R-260 Grade asymmetric rail into symmetric, 60 kg UIC/60E1 & IRS 52 Kg rail section for making of thick web switches / thick web switch expansion joints.

#### 2.0 MANUFACTURING PROCESS

2.1 The end forging of asymmetric rail shall be carried out by an automatic closed die forging process. Heating for forging purpose shall be done in automatically controlled induction heating furnace with controlled atmosphere. In case of multi stage forging change of dies should be automatic preferably. At the end of the forging, the forgings should require very little or no straightening to avoid introduction of residual stresses in the end forged portion. The forging press shall be of adequate capacity for achieving the designed profiles.

#### 3.0 FORGING OF RAIL-ENDS

- 3.1 The rails satisfying the stipulations specified above shall only be used for forging minimum length of forged section with desired rail profile shall be 500mm at web and 470 mm at foot and transition length of forging shall be in the range of 150-200mm for 60 Kg/60 E1 rail profile. The minimum length of forged section with IRS 52 Kg rail profile shall be 380 mm at web and 350 mm at foot and transition length of forging shall be in the range of 175-200mm.
- 3.2 Drawing of asymmetrical rail along with proposed forging details shall be submitted by supplier and same will be approved by RDSO before forging of rail.
- 3.3 The end forging shall be done by pressure die forging. The forged portion shall be smooth and variation in cross section in the transition portion shall be

uniform without notches, dents, projections or surface flaws. There shall be no internal defects, no cracks or overlaps in the forged portion which shall be tested for internal defects by Ultrasonic Testing and for cracks/flaws by Dye-Penetrant Test (DPT)/ Magnetic Particle Test (MPT).

#### 3.4 Testing on forged rail

- 3.4.1 Geometrical Check- 100% on forging and machined end profile.
- 3.4.2 Ultrasonic Test 100% forged rail (in the forged area & heat affected area).
- 3.4.3 DP/Magnetic Particle Test 100% forged rail (in the forged and heat affected area).


#### 3.5 Hardness test

- 3.5.1 In the initial stage of establishment of a plant, hardness tests shall be conducted on 3 places of end forged rails which have passed the geometrical requirements, Ultrasonic test requirements and other non-destructive tests.
- 3.5.2 Hardness shall be measured along the center line of the head in the forged portion for the length as per following break up:
  - a) Entire forged portion of UIC-60/60 E1 & IRS 52 Kg rail section
  - b) Entire transition portion
  - c) At least 400mm of length on ZU-1-60/60E1A1 & ZU-2-49/49E1A1 rail section from transition zone end of ZU-1-60/60E1A1& IRS 52 Kg
- 3.5.3 The hardness shall be measured at an interval of 10mm along the center line.
- 3.5.4 After recording the measurements, the top layer of 5mm thickness shall be removed and the hardness shall be measured again, 5mm below of surface of rail, in a manner described at 3.5.1 to 3.5.3 above.
- 3.5.5 Hardness in the forged portion shall not be lower than the hardness of the rolled rail portion (ZU-1-60/60E1A1) & ZU-2-49/49E1A1 (260 BHN min). In the transition area and heat affected zone, lower hardness is acceptable but at no point in this area the hardness should go more than 40 BHN lower than the hardness of parent rail. Further, the length of such low hardness zone shall not be more than 50mm. All the 3 samples shall meet the requirements.
- 3.5.6 In case the criteria stated at 3.5.5 above is not met, the forging process shall be reviewed, improvements be carried out and fresh tests for hardness be conducted as per Para 3.5.1 to 3.5.5 above.
- 3.5.7 The data generated as per 3.5.1 above shall be used to identify the spots that are critical from hardness consideration, 3 such spots will be identified for measurement of hardness on each and every piece at surface of the rail table.

- 3.5.8 Once the process is established, one sample out of every 500 forgings will be tested for hardness in the manner described at Para-3.5.1 to 3.5.5 above.
- 3.5.9 At this stage, only one sample needs to be drawn as against 3 stipulated for the initial stage.
- 3.5.10 In case the sample fails to meet the criteria stipulated at 3.5.5 above, the forging process shall be reviewed, improvements be carried out and fresh tests for hardness be conducted as per Para 3.5.1 to 3.5.5 above.
- 3.5.11 Every forging shall be subjected to hardness tests on the surface of rail table at 3 points identified as per Para 3.5.7 above.
- 3.5.12 Hardness of forged section shall not be lower than the hardness of the rolled rail portion (ZU-1-60/60E1A1 & ZU-2-49/49E1A1). In the transition area lower hardness is acceptable but at no point in this area the hardness should go more than 40 BHN lower than the hardness of parent rail. In case these requirements are not met, the forging shall be rejected.

#### 3.6 Micro Structure

3.6.1 The micro structure shall be pearlitic but grain boundary ferrite may occur in these grades. The maximum grain boundary ferrite permitted is shown in the Figure shown below (Ref : EN 13674-2: 2006). There shall be no martensite, bainite or grain boundary cementite.

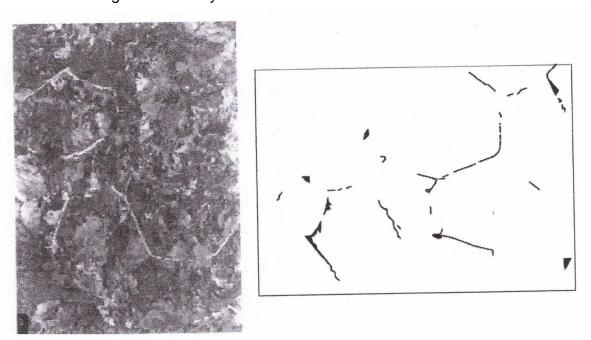

Photomicrograph x 500

Figure: Photomicrograph and diagram showing maximum allowable ferrite at the Grain boundaries

- 3.6.2 Microstructure analysis should be carried out for one forging per 500 forgings done.
- 3.6.3 For the purpose, end of tensile test piece shall be used and structure will be seen on the transverse section.

#### 3.7 Tensile Test

Tensile test shall be done on the symmetrical portion of the forged rail, if straightening operation is carried out, tensile test will be done after straightening.

This test shall be conducted as per clause 17 of IRS-T-12-2009, as amended from time to time. The frequency of the test shall be 1 in 500.

3.8 All the above, mentioned tests in forged portion of rail will be carried out in manufacturers premises in the presence of purchaser's representative.

#### 3.9 Tolerances

The tolerances on dimensions and end straightening of end forged rail shall comply with relevant clauses of IRS:T-12-2009 (clause 9), as amended from time to time. Forged rail shall pass at least in 'B' class category as mentioned in Clause 9.4.1 & 9.4.2 of IRS T-12-2009, as amended from time to time.

#### 4.0 IDENTIFICATION

Each and every rail shall be given an identification heat number which shall be painted on the non-forged area of the rail. Record shall be maintained to link the rail, by its identification number to the cast number of the rail given by the rail manufacturer. The identification number shall be used for the traceability of the rail for all internal quality records and operations. Further, for easy identification, each TWA rail End Forged to 60E1 profile rail shall have legible unique identification, punched at the foot of end forged length.

The Unique Identification shall to be given as ABCMMYYXXXXX, where,

ABC = first, second & third character will denote "Firm's Initial"

MM = fourth & fifth character will denote "Month of forging"

YY = sixth & seventh character will denote "Year of forging"

XXXXX = eighth, ninth, tenth, eleventh & twelfth character will denote

"Serial number of forging", starting from 00001 every calendar year.

#### 5.0 FINAL FINISHING

The area of cross section on the entire forged portion shall be adjusted to the required measurements by machining. Final finishing of the forged transition shall be performed by CNC Milling Machine. The manufacturer shall submit gauges for checking the cross sectional dimensions for approval to RDSO. Complete decarburized surface created due to heating and forging process to be removed up to 60Kg UIC/60E1 & ZU-2-49/49E1A1 rail profile and beyond that only on head table by milling operation. No black spots etc. will be seen after machining operation.

6.0 Inspection Regime for End Forged Thick Web Asymmetrical (TWA) Rail of ZU-1-60/60E1A1& ZU-2-49/49E1A1 Rail Profile (Grade 880/R260), arranged by Thick Web Switch /Thick web switch expansion joints manufacturer, shall be as detailed in Annexure-A of this specification.

## Inspection Regime for End Forged Thick Web Asymmetrical (TWA) Rail of ZU-1-60/60E1A1 & ZU-2-49/49E1A1 Rail Profile (Grade 880/R260)

Following are the different inspection stages as per which the inspection is to be done

- 1. Inspection of TWA Rail of ZU-1-60/60E1A1 & ZU-2-49/49E1A1 rail profile on receipt at End Forging Plant.
- 2. Inspection at End Forging Plant of process approval to be done generally once for a particular plant (03 samples for initial 500 forgings).
- 3. Inspection of End of TWA Rail of ZU-1-60/60E1A1 & ZU-2-49/49E1A1 rail profile into 60kg UIC/60E1 & IRS 52 Kg rail section respectively process approval (at End Forging Plant)
- 4. Inspection of End Forged TWA Rail at the works premises of Thick Web Manufacturer

These inspections stages detailed below.

1.	1. Inspection of TWA Rail of ZU-1-60 /60E1A1 & ZU-2-49/49E1A1 rail profile on receipt at End Forging Plant										
SL No.	Stage	Process (Inspection Parameters)	Acceptance standards & Reference document	Sample size and frequency of inspection/te sting wherever applicable		Rejection details					
1.1	Scrutiny of Test Results submitted by manufacturer of Asymmetrical rail of ZU-1- 60/60E1A1 & ZU- 2-49/49E1A1 rail profile	Criteria Test as prescribed in IRS-T-12-2009:  1. Residual Stress measurement 2. Fracture Toughness measurement 3. Fatigue Test 4. Fatigue Crack Growth Rate Test	12-2009 amended from time to time	100%	Before taking up end forging – QC organization of End forging plant. QC organization of Thick Web Switch/Thick Web Switch expansion joints Manufacturer	End Forging not to be taken up for TWA rail not conforming to IRS-T-12-2009 amended from time to time					
		Test Result for Acceptance tests as	As per IRS-T- 12-2009	100%	may also do						

		prescribed in IRS-T-12-	amended from		the	
		2009: amended from time	time to time		inspection.	
		to time:				
		Chemical Analysis				
		2. Tensile Test				
		3. Sulphur Print				
		4. Hardness Test				
		5. Falling Weight Test				
		6. Hydrogen Content				
		7. Inclusion Rating Level				
		8. Decarburisation Test				
		(For R260)				
		9. Determination of total				
		oxygen content (for				
		R260)				
		Test Results for freedom	As per para 10	100%		
		from defects including	of IRS-T-12-			
		surface defects, defects as	2009 amended			
		per UFSD Testing, eddy	from time to			
		current testing etc.	time			
		T . D . II . O . II		1000/		
		Test Result for Sections &	As per para 9 of	100%		
		Dimensions	IRS-T-12-2009			
			amended from			
1.0	In an action	All Information montions	time to time	1000/	Defere telding	Fod Foreign pot to be
1.2	Inspection of		As per IRS-T-	100%	Before taking	End Forging not to be
	marking provided for Rail	at para 8 of IRS-T-12-2009 amended from time to time	12-2009 amended from		up end	taken up for TWA rail
	Identification		time to time		forging – QC	not conforming to IRS- T-12-2009 amended
	iueniincalion	should preferably be			organization of End	from time to time
		included in the marking at TWA	and/or as per manufacturer's			non une to ume
		IVVA			forging plant. QC	
			specification		-, -	
					organization of Thick Web	
					Switch /	
					Thick Web	
					Switch	
					OWILLII	

		expansion joints Manufacturer may also do the inspection.
1.3	Any test mentioned above or any other test deem joints manufacturer for confirmation of test results	ed fit by End forging Plant/Thick Web Switch /Thick Web Switch expansion submitted by TWA Rail manufacturer.

SL No.	Stage	Process (Inspection Parameters)	Acceptance standards & Reference document	Sample size and frequency of inspection/testing wherever applicable	Inspection by	Rejection details
2.1	Visual Inspection & Final Finishing	Surface Defects (The forged portion shall be smooth and variation in cross section in the transition portion shall be uniform without notches, dents, projections or surface flaws)  Milling of forged portion (Complete decarburized surface created due to heating and forging process to be removed up to 60 Kg UIC/60E1 & IRS 52 Kg rail profile and	web asymmetric rails.	All 03 samples	QC organization of End forging plant	End forgings not conforming to specification shall be rejected. Another sample should be produced and tests carried out.

		beyond that only on				
		head table by milling				
		operation. No black				
		spots etc. will be				
		seen after machining				
		operation)				
2.2	Geometrical	Minimum forged		All 03 samples		
	Check	length 500 mm at				
		web and 470 mm at	,			
		foot of 60 kg/60E1	(IRS:T-62)			
		profile and transition				
		length 150-200 mm.				
		Minimum forged				
		length 380 mm at				
		web and 350 mm at				
		foot of IRS 52 kg				
		profile and transition				
		length 175 mm-200 mm.				
		Dimensional check of	IRS-T-12/2009	All 03 samples		
		60 kg profile (Class		All 03 samples		
		B) & IRS 52 Kg				
		(Class B)	ume			
2.3	Ultrasonic	Internal defects	Ultrasonic Testing	All 03 samples		
	Testing in the		shall be done as per	7 00 00p.00		
	end forged		Chapter 10 of Manual			
	portion,		for Ultrasonic Testing			
	transition		of rails and Weld,			
	portion and		revised 2012 issued			
	heat affected		by RDSO.			
	area		•			
2.4	Dye-Penetrant	No cracks or	IRS Specification for	All 03 samples	QC	End forgings
	Test (DPT) or	overlaps in the forged	end forging of thick	·	organization	not conforming
	Magnetic	area	web asymmetric rails		of End	to specification
	Particle Test		(IRS:T-62)		forging	shall be
	(MPT)				plant	rejected
						Another sample

2.5	Hardness Test	Measurement of hardness at rail top and 5 mm below rail top to identify 3 spots critical from hardness consideration for measurement of hardness on each forging at surface of rail table.	web asymmetric rails (IRS:T-62)			should be produced and tests carried out
2.6	Tensile Test	UTS, Yield Strength & Elongation	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62) & as per IRS-T-12-2009 amended from time to time	1 Sample randomly selected out of 03 samples		
2.7	Micro-structure	Microstructure	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62)			
2.8	Identification mark of forging	Identification no. etc	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62) or as per specification end forging plant	All 03 samples	QC organization of End forging plant	Not Applicable

- 2.9 The test report for tests/checks made as described above should be submitted to the inspecting agency for scrutiny and approval.
- 2.10 After identification of 03 spots critical from hardness consideration during process approval which is valid for initial 500 forgings, one sample out of every 500 forgings (against 03 stipulated for initial testing) shall be tested for hardness as given in para 3.5.8 to 3.5.10 of specification for end forging of thick web asymmetric rails (IRS:T-62) and test result communicated to inspecting agency.

3. Inspection of End Forging of TWA Rail of ZU-1-60/60E1A1 & ZU-2-49/49E1A1 rail profile into 60kg UIC /60E1 & IRS 52 Kg Rail section respectively after process approval (at End Forging Plant) SL Stage **Process** Sample size Inspection by Rejection details Acceptance No. (Inspection and frequency standards & Parameters) Reference of inspection/testi document ng wherever applicable IRS Specification for QC 3.1 Visual Surface Defects 100% End forgings not inspection end forging of thick organization of conforming to specification Milling of forged Final Finishing shall be rejected. web asymmetric End Forging portion Plant rails (IRS:T-62). 100% 3.2 Geometrical Minimum forged IRS Specification for end forging of thick check length 500 mm at asymmetric web and 470 mm web at foot of 60 rails kg/60E1 (IRS:T-62). and transition length 150-200 mm Minimum forged length 380 mm at web and 350 mm at foot of IRS 52 kg profile and transition length 175 mm-200 mm. 100% Dimensional IRS-T-12/2009 check of amended from time

100%

60kg/60E1 profile

(class B) & IRS 52 Kg (Class B)

Internal defects

3.3

Ultrasonic

end

portion,

transition

Testing in the

forged

to time

Ultrasonic

chapter

shall be done as per

testing of rails and

10 Manual for ultrasonic

Testing

	portion and heat affected area		weld revised 2012 issued by RDSO.			
3.4	Dye-Penetrant Test (DPT) or Magnetic Particle Test (MPT)	No Cracks or overlaps in the forged area	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62).	100%		
3.5	Hardness Test	Measurement of hardness at three locations identified during process approval using portable tester (also refer 2.10 for measurement of hardness after initial 500 forgings as stipulated in para 3.5.8 to 3.5.10 of RDSO specification for end forging)		100%	QC organization of End Forging Plant	End forgings not conforming to specification shall be rejected.
3.6	Tensile Test	UTS, Yield Strength & Elongation	IRS Specification for end forging of thick web asymmetric rails(IRS:T-62) and as per IRS-T-12- 2009 amended from time to time		QC organization of End Forging plant	In case test piece fails, two more test pieces shall be made from same end forged rail, Both the test pieces should pass the test otherwise entire lot shall be rejected.
3.7	Micro-structure	Microstructure	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62).			•

				3.6.3 of this specification)		
3.8 Identification mark of the second	tion Identification etc	no.	IRS Specification for end forging of thick web asymmetric rails (IRS:T-62).		QC organization of End Forging plant	Marking to be done

# 4. Inspection of End Forging of TWA Rail at the premises of Thick Web Switch / Thick web switch expansion joints Manufacturer

SL No.	Stage	Process (Inspection	Acceptance standards &	Sample size and frequency of	Inspect	ion by	Rejection details
		Parameters)	Reference document	inspection/testin g wherever applicable	Internal	RDSO	_ dotallo
4.1	Scrutiny of Test Results submitted by manufacturer of Asymmetrical rail of ZU-1- 60/60E1A1 & ZU-2- 49/49E1A1 rail profile	All parameters mentioned at SI. No. 1.1 & 1.2	As per IRS-T-12- 2009 amended from time to time	100%	QC organization of Thick Web Switch /Thick Web Switch expansion joint manufacturing of thick web switches/ Thick Web Switch expansion joints	100%	Rejected if not conforming to specificatio n
4.2	Scrutiny of Test Results of end forging of TWA rail of ZU-1- 60/60E1A1&ZU- 2-49/49E1A1 rail profile to 60 kg UIC /60 E1A1 & IRS 52 Kg rail section respectively			100%			

4.3	Tests on TWA	Chemical Test	As per IRS-T-12-	1 rail sample out	QC	100%	In case,
	Rail of ZU-1-60	Tensile Test	2009 amended	of every 10 heats	organization of	witnessing by	test of the
	rail profile	Tensile Test	from time to time	or TWA rail or part	Thick Web	RDSO	rail sample
				thereof	Switch /Thick Web Switch		fails, the more test
					expansion joint		pieces shall
					manufacturing		be made
					of thick web		from same
					switches/ Thick		rail sample.
					Web Switch		Both the
					expansion joints		test pieces
							should pass
							the test
							otherwise rails of that
							particular
							heat shall
							be rejected.
							In addition
							a sample
							each of the
							balance
							heats shall
		Sections &		100%	100% by QC	Witnessing	be tested.  Rejected if
		Dimensions		10070	organization of	/cross	not
4.4	Ultrasonic Test	Internal defect	Ultrasonic Testing	100%	Thick Web	verification :	conforming
	of TWA rail of		shall be done as		Switch / Thick	20% by	to
	ZU-1-		per Chapter 10 of		Web Switch	RDSO (In	specificatio
	60/60E1A1 &		Manual for		expansion joints	case of	n
	ZU-2-		Ultrasonic Testing		Manufacturer	discrepancies	
	49/49E1A1 Rail		of rails and welds,		before taking up	, 100%	
	profile along with end forged		revised 2012 issued by RDSO		manufacturing of thick web	witnessing/cro ss-verification	
	portion		leaden by KDOO		switches/ Thick	shall be done	
4.5	Visual	Surface Defects	IRS	100%	Web Switch	by RDSO	
	Inspection &	23.1400 20.000	specification for	10070	expansion joints	.,	
			'		, ,		

	Final Finishing of end forging portion	Milling of forged portion	end forging of thick web asymmetric rails (IRS:T-62)		
4.6	Geometrical check of end forged portion	Minimum forged length 500mm at web and 470 mm at foot of 60 kg/60E1 profile and transition length 150-200mm	IRS-T-12/2009 amended from	100%	
		Minimum forged length 380 mm at web and 350 mm at foot of IRS 52 kg profile and transition length 175 mm-200 mm			
		Dimensional check of 60kg/60E1 profile (class B) & IRS 52 kg profile (class B)			
4.7	Dye-Penetrant Test (DPT) or Magnetic Particle Test (MPT)	No Cracks or overlaps in the forged area	IRS specification for end forging of thick web asymmetric rails (IRS:T-62)	100%	
4.8	Hardness Test of end forged portion	Measurement of hardness at three locations identified during	IRS specification for end forging of thick web	100%	

4.9	Tensile Test of end forged portion	process approval using portable hardness tester UTS, Yield Strength & Elongation	asymmetric rails (IRS:T-62)  IRS specification for end forging of thick web asymmetric rails	1 per 500 forgings (Minimum 1 per lot if lot size<= 500 forgings)	100% by QC organization of Thick Web Switch / Thick Web Switch	100% witnessing shall be done by RDSO	In case test piece fails, two more test pieces shall be
4.10	Micro-structure of end forged portion	Microstructure	(IRS:T-62) IRS specification for end forging of thick web asymmetric rails (IRS:T-62)	1 per 500 forgings (Minimum 1 per lot if lot size <= 500 forging) End of tensile test piece may be used as para 3.6.3 of this specification	expansion joints Manufacturer before taking up manufacturing of thick web switches/ Thick Web Switch expansion joints		made from same end forged rail, Both the test pieces should pass the test otherwise entire lot shall be rejected
4.11	Identification mark on TWA rail and at end forging portion	Identification no. etc	IRS-T-12/2009, amended from time to time, TWA Rail Manufacturer's specification &IRS specification for end forging of thick web asymmetric rails (IRS:T-62)	100%	100% by QC organization of Thick Web Switch Manufacturer before taking up manufacturing of thick web switches	Witnessing /cross verification : 20% by RDSO (In case of discrepancies , 100% witnessing/cro ss-verification shall be done by RDSO	Making to be done

Note:- Section/s of Thick web Asymmetrical rails not covered in IRS /T-12 Should conform to UIC/EN standard.